arXiv:1610.06152v1 [cond-mat.mtrl-sci] 19 Oct 2016

Impact of Intermediate Sites on Bulk Diffusion Barriers: Mg Intercalation in $Mg_2Mo_3O_8$

Gopalakrishnan Sai Gautam,[1,2,3,*] Xiaoqi Sun,[4,†] Victor Duffort,[4] Linda F. Nazar,[4] and Gerbrand Ceder[2,3,‡]

[1] *Department of Materials Science and Engineering, Massachusetts Institute of Technology, Cambridge, MA 02139, USA*
[2] *Materials Science Division, Lawrence Berkeley National Laboratory, Berkeley, CA 94720, USA*
[3] *Department of Materials Science and Engineering, University of California Berkeley, CA 94720, USA*
[4] *Department of Chemistry and the Waterloo Institute of Nanotechnology, University of Waterloo, ON N2L3G1, Canada*

The ongoing search for high voltage positive electrode materials for Mg batteries has been primarily hampered by poor Mg mobility in bulk oxide frameworks. Motivated by the presence of Mo_3 clusters that can facilitate charge redistribution and the presence of Mg in a non-preferred (tetrahedral) coordination environment, we have investigated the Mg (de)intercalation behavior in layered-$Mg_2Mo_3O_8$, a potential positive electrode. While no electrochemical activity is observed, chemical demagnesiation of $Mg_2Mo_3O_8$ is successful but leads to amorphization. Subsequent first-principles calculations predict a strong thermodynamic driving force for structure decomposition at low Mg concentrations and high activation barriers for bulk Mg diffusion, in agreement with experimental observations. Further analysis of the Mg diffusion pathway reveals an O–Mg–O dumbbell intermediate site that creates a high Mg^{2+} migration barrier, indicating the influence of transition states on setting the magnitude of migration barriers.

Rechargeable Mg batteries have received interest as an energy storage system that potentially offers high energy density. The major advantage relies on the benefits of Mg metal as the negative electrode, which, in addition to being inexpensive, abundant and safe in handling and storage, also provides high volumetric capacity (3833 mAh cm^{-3}) and can be free of dendrite growth when operating in an electrochemical cell.[1–3] However, the development of corresponding positive electrode materials has been slow.[2] Since the discovery of the first seminal functional Mg insertion positive electrode – the Chevrel phase (CP, Mo_6S_8),[4] only recently have two other structures been shown to be suitable for Mg (de)intercalation in a full cell arrangement with a Mg anode, namely the spinel and layered titanium sulfide.[5,6] The above materials take the advantage of a "soft" anionic framework that interacts weakly with the Mg^{2+} and assist its mobility. On the contrary, sluggish multivalent ion mobility is generally observed in oxide lattices. Nevertheless, oxides are still of great interest due to their potentially higher operating voltage.[7–15]

Levi *et al.* have speculated that the presence of Mo_6 clusters in the CP structure is one of the key factors for facile Mg^{2+} mobility by promoting charge redistribution.[8] The possibility that a similar principle may apply to oxides guided us to $Mg_2Mo_3O_8$ (Figure 1a), which has Mo_3 clusters in the Mo_3O_8 layers (Figure 1b).[16,17] In this structure, Mg occupies both octahedral and tetrahedral sites between the layers. While octahedral Mg share both edges and corners with MoO_6 octahedra (Figure 1a), tetrahedral Mg share corners with MoO_6 and MgO_6 octahedra. Since Mg is also present in a "non-preferred" tetrahedral coordination (Figure 1a),[18] a Mg diffusion pathway with lower migration barriers is expected than when Mg is exclusively found in its preferred octahedral coordination,[9] such as in conventional layered oxides. In the case of layered oxides, the Mg diffusion pathways contain an intermediate tetrahedral site presumably with high energy relative to the stable octahedral site, leading to poor Mg mobility.[9]

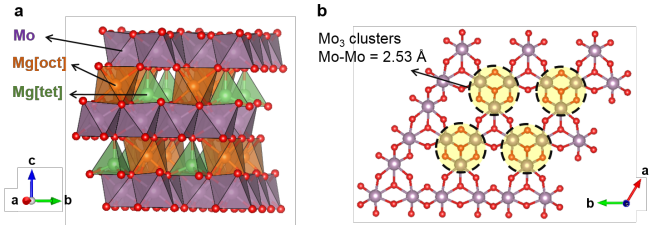

FIG. 1: (a) Crystal structure of $Mg_2Mo_3O_8$. (b) MoO_6 octahedra layer showing Mo_3 clusters.

We note that the Li analogue ($Li_4Mo_3O_8$) has previously been examined in a Li cell, offering 218 mAh g^{-1} initial specific capacity.[19] Other materials with similar structures containing Mo_3 clusters, such as $LiMoO_2$ and Li_2MoO_3, also function well as Li-ion positive electrodes.[19–21] On the other hand, only limited work has been done for Mg intercalation in Mo-oxides,[12,22,23] motivating us to examine the Mg^{2+} diffusion properties in $Mg_2Mo_3O_8$ and its potential to be a positive electrode material for Mg batteries.

$Mg_2Mo_3O_8$ was obtained by solid-state synthesis (see Electronic Supporting Information – ESI*#) and provided particles a few micrometers in size (Figure 2a). Its X-ray diffraction (XRD) pattern was indexed in the

*# Electronic Supporting Information available free of charge online at http://dx.doi.org/10.1039/C6TA07804D

$P6_3mc$ space group characteristic of this material (Figure 2b). In order to study the possibility of Mg removal from such a structure, chemical demagnesiation was carried out using NO_2BF_4, a commonly used oxidizing agent for chemical delithiation.[24] $Mg_2Mo_3O_8$ and NO_2BF_4 were reacted in a 1:4 ratio, which would allow complete Mg de-intercalation if each NO_2BF_4 sustained a one electron reduction as anticipated. Energy dispersive X-ray spectroscopy (EDX) reveals that the majority of the Mg was removed from the structure (Table I). The particles become smaller after demagnesiation (Figure 2c), suggesting some changes in the material. Despite these differences, the XRD results indicate no shift of the peaks (Figure 2d). The atomic positions obtained by Rietveld refinement[25] are almost the same as the pristine (Table S1 in ESI), suggesting that a two-phase reaction takes place, with the demagnesiated phase being amorphous. During this process, Mg is presumably first removed from the outer shell, leading to the destabilization of the parent lattice and eventual amorphization. The amount of amorphous phase in the demagnesiated product is estimated to be around 87 wt% using Si as an external standard method (Figure 2d, see ESI for details), giving an overall composition of $Mg_{0.24}Mo_3O_8$, which is similar to the cationic ratio determined by EDX (Table I) and indicates complete demagnesiation of the amorphous component. The $\sim$ 13 wt% unreacted $Mg_2Mo_3O_8$ results from the reduced oxidizing strength of NO_2BF_4 exhibited near the end of the reaction due to low oxidizer concentration, or other side reactions. Partial demagnesiation from $Mg_2Mo_3O_8$ was not achieved when the ratio of oxidizing agent was reduced ($Mg_2Mo_3O_8$:NO_2BF_4 = 1:2), as indicated by the preservation of the initial phase obtained by XRD refinement (Figure S1a and Table S1c). Together with the decrease of overall Mg concentration (Mg/Mo ratio of $\sim$ 0.53(4)/3 by EDX) and the co-existence of different morphologies (Figure S1b), the XRD data suggests that part of $Mg_2Mo_3O_8$ undergoes complete demagnesiation and becomes amorphous with some fraction of material not participating in the reaction.

TABLE I: EDX results of $Mg_2Mo_3O_8$ before and after chemical demagnesiation.

Sample	Pristine	Demagnesiated
Mg/Mo	1.59(4)/3	0.13(6)/3

Since the degree of chemical oxidation was hard to control, we attempted to evaluate stepwise demagnesiation behavior by an electrochemical method. As it has been suggested that the Mg desolvation process depends on the solvent,[26,27] and this is critical for the electrochemical mechanism at the positive electrode,[28,29] $Mg_2Mo_3O_8$ was examined in both non-aqueous (all phenyl complex – APC[30]) and aqueous ($Mg(ClO_4)_2$ in water) systems. A demagnesiation voltage similar to the delithiation of $Li_4Mo_3O_8$ (average of $\sim$ 2.4 V vs. Mg),[19] or at $\sim$ 2.6 V as predicted by first principles calculations (Figure S4, see ESI for details) could be expected. Both electrolytes offer a stable voltage window for this range; however, no electrochemical activity was observed in either system (Figure S2). Such results potentially indicate the existence of a high Mg^{2+} diffusion barrier in the structure, hence kinetics being the main limitation. Chemical oxidation, on the other hand, might involve a mechanism other than simple cation diffusion, such as a partial dissolution/re-precipitation process. This helps in lowering the kinetic barrier and establishes successful Mg removal.

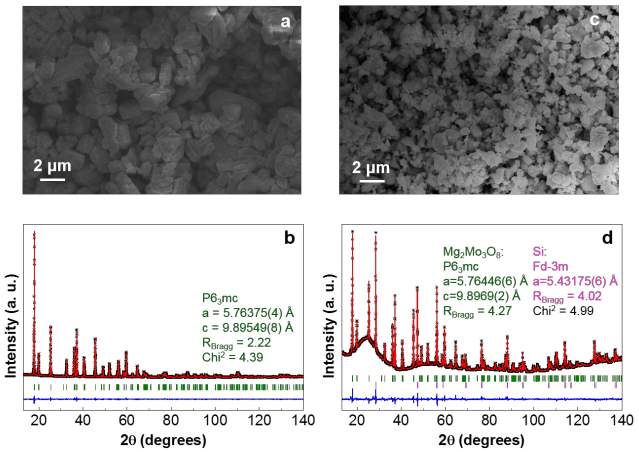

FIG. 2: (a) SEM image and (b) Rietveld refinement fit of pristine $Mg_2Mo_3O_8$ (Bragg-Brentano geometry). (c) SEM image of the demagnesiated sample. (d) Rietveld refinement of the demagnesiated sample with external silicon standard added to evaluate the percentage of amorphous phase. The mixture was sealed in X-ray capillary under Ar and was measured in Debye-Scherrer geometry. Black crosses – experimental data, red lines – fitted data, blue line – difference map between observed and calculated data, green ticks – the $P6_3mc$ phase of $Mg_2Mo_3O_8$, pink ticks – the $Fd\bar{3}m$ phase of Si.

In order to understand the amorphization upon chemical demagnesiation and rationalize the lack of electrochemical activity in $Mg_2Mo_3O_8$, we carried out first principles calculations to determine the energy above hull (E^{hull}) indicating the stability of the structure, and the activation barriers for Mg diffusion within the structure (methodological details of the calculations are provided in the ESI).

The energy above the convex ground state hull (E^{hull}) of the $Mg_xMo_3O_8$ structure, calculated with respect to the stable compounds in the Mg-Mo-O ternary phase diagram, can be used to evaluate the thermodynamic stability of the structure on demagnesiation.[13,15] Typically, a thermodynamically stable structure will have an E^{hull} of 0 meV/atom, while more positive E^{hull} values indicate greater driving force to form other phases, which may be reflected as difficulty in synthesizing a compound, or as decomposition during (de)intercalation. Also, E^{hull} values are evaluated at 0 K and entropic contributions can stabilize a structure at higher temperatures. The

values listed in Table II have been determined from the available compounds in the Materials Project database.[31] The trends in Table II indicate an increasing E^{hull} with increasing Mg removal from the $Mg_2Mo_3O_8$ structure, corresponding to an increase in the thermodynamic driving force for decomposition. The E^{hull} values at lower Mg concentrations are very high – consistent with the experimentally observed amorphization during chemical Mg extraction from $Mg_2Mo_3O_8$ (Figure 2) and the naturally amorphous occurrence of Mo_3O_8.[32,33]

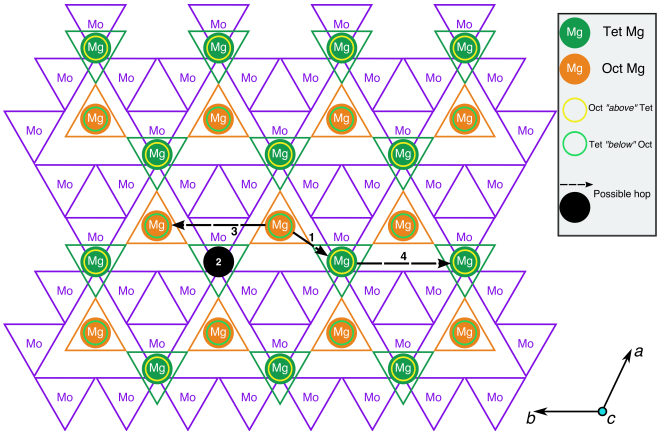

FIG. 3: A 2D-view of the $Mg_2Mo_3O_8$ structure perpendicular to the layer spacing direction (c-axis) is shown. Purple, green and orange triangles indicate MoO_6 octahedra, Mg tetrahedra and Mg octahedra, respectively. The yellow and green circles correspond to octahedral and tetrahedral Mg atoms across a Mo-plane. The black circles and arrows indicate possible Mg→Mg hops within the structure.

To evaluate Mg mobility in the $Mg_2Mo_3O_8$ structure, the possible Mg diffusion hops within the structure were determined. Being a layered structure, $Mg_2Mo_3O_8$ can be visualized on a 2D-plane, as shown in Figure 3, with octahedral Mo, tetrahedral Mg and octahedral Mg indicated by purple, green and orange triangles, respectively. The four possible Mg→Mg hops that can occur in the structure are illustrated by the black circle and arrows in Figure 3. Three hops (black arrows) occur in the same Mg-plane and the fourth hop (black circle) moves Mg across a Mo-plane. The shortest hops (type 1 and 2) span ∼ 3.38 Å and ∼ 4.33 Å, respectively, and involve Mg migration from a tetrahedral site to an octahedral site (or vice-versa), while hops 3 and 4 are ∼ 5.76 Å in distance and involve Mg jumps between similarly coordinated sites (oct → oct or tet → tet). Although hops 3 and 4 are direct between octahedral or tetrahedral Mg sites, they are likely to be constituted by two consecutive hops of type 1 (i.e. an oct → tet hop followed by a tet → oct hop and vice-versa). Alternate routes for hops 3 and 4 are not possible due to intermediate Mg tetrahedral sites, which will face-share with MoO_6 octahedra and experience strong electrostatic repulsions as a result. Hence, hops 1 and 2 are the relevant Mg migration pathways that need to be considered in calculations.

Figure 4a displays the calculated Mg migration barriers (at $x_{Mg} \sim 2$ with dilute vacancy limit) along the hop 1 (black) and 2 (red) pathways, with the respective hop distances normalized on the x-axis. Both hops begin at a tetrahedral Mg and terminate at an octahedral Mg, explaining the difference in energy between the end points (∼ 250 meV). Notably, Mg mobility along both hops 1 and 2 is expected to be poor, given the large migration barriers (∼ 1200 meV and ∼ 2000 meV for hops 1 and 2, respectively), compared to the 525 – 650 meV required for bulk Mg mobility at reasonable rates.[9] The high migration barriers also explain the lack of electrochemical activity observed. Nevertheless, if any Mg migration is observed in the structure, the Mg^{2+} ions are likely to diffuse along the in-plane hop 1 pathway.

While the high barrier for hop 2 is due to the strong electrostatic repulsion Mg experiences from Mo atoms as it passes through a triangular face of oxygen atoms across the Mo_3O_8 layer, a closer look into hop 1 is required to understand the large barriers. Visualization of the Mg migration along hop 1 is given in Figure 4b, with intermediate sites and their respective energies (in Figure 4a) indicated by the numbered circles. Sites 1, 2 and 3 respectively correspond to the O–Mg–O "dumbbell" configuration,[9] the intermediate metastable tetrahedral site (yellow) and the triangular face between the intermediate tetrahedral and stable octahedral sites. While site 3 (triangular face, Figure 4b) has an energy of ∼ 685 meV with respect to the tetrahedral site (similar to ∼ 600 – 800 meV observed in oxide spinels[15]), the magnitude of the barrier is determined by site 1, where Mg is situated along an O–O bond (edge of the stable tetrahedron), in a dumbbell configuration. Previous evaluations of Mg migration through an O–O dumbbell hop for layered NiO_2 have reported high barriers (∼ 1400 meV),[9] similar to the value reported in this work.

Although the O–Mg–O dumbbell hops are precluded from occurring in usual cathode materials[9,10] due to the presence of alternate low-energy pathways, no such possibility exists for Mg migration in the $Mg_2Mo_3O_8$ structure. For example, an alternate pathway for hop 1 that avoids the O–Mg–O dumbbell is shown in Figure 4c. The intermediate octahedral (dark blue) and tetrahedral (yellow) sites in Figure 4c share a triangular face with the stable tetrahedral (green) and octahedral (orange) sites, respectively. Additionally, each intermediate site also shares a triangular face with a MoO_6 octahedron (blue polyhedron, Figure 4c). While an intermediate Mg octahedron that face-shares with a higher valent transition metal octahedron need not preclude Mg migration, the intermediate tetrahedral site (yellow site, Figure 4c) will experience much stronger electrostatic repulsion from the face-sharing MoO_6 octahedron, subsequently increasing its energy and preventing any potential Mg migration. Indeed, Mg migration calculations initializing hop 1 as displayed in Figure 4c relax to a path similar to the O–Mg–O hop (Figure 4b) with a similar barrier (∼ 1150 meV, Figure S5). Notably, scenar-

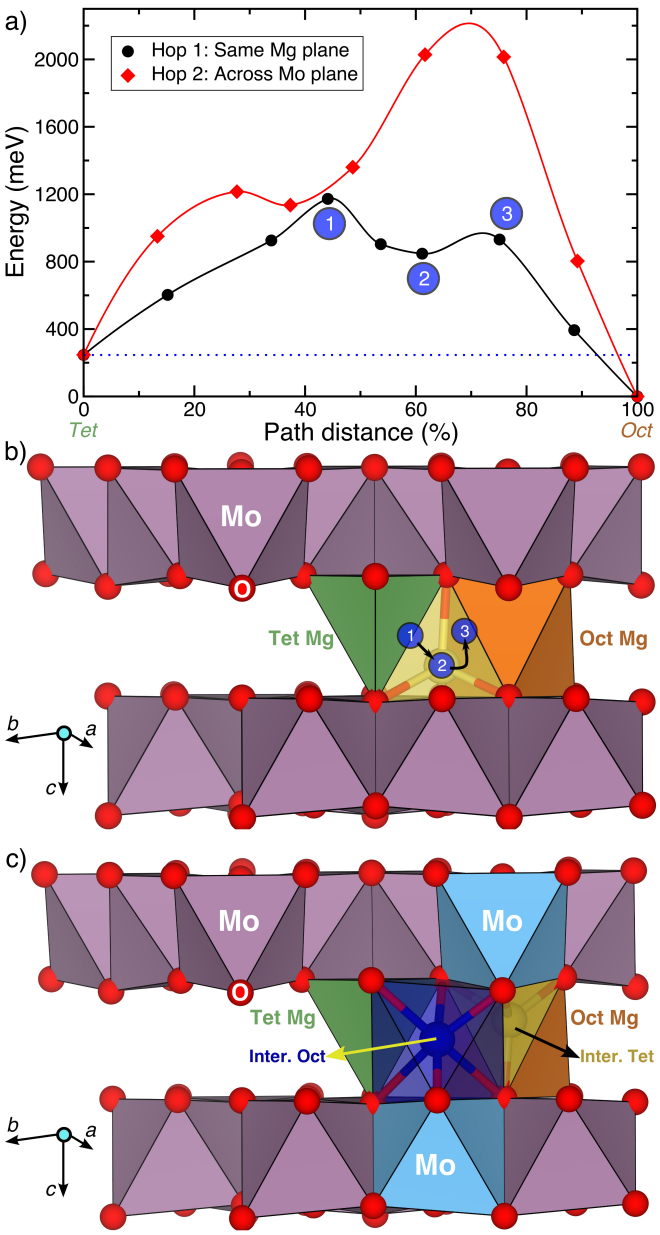

FIG. 4: (a) The activation barrier for Mg diffusion along hops 1 and 2 in the $Mg_2Mo_3O_8$ structure, with the normalized path distance on the x-axis. (b) A closer view of hop 1, where the numbered circles correspond to various intermediate sites along the hop as labeled in (a). The intermediate tetrahedral site, which is edge-sharing with the stable tetrahedral site (green), is indicated in yellow. (c) An alternate pathway for hop 1 that involves intermediate octahedral (dark blue) and tetrahedral (yellow) sites, which are face-sharing with the stable tetrahedral (green) and octahedral (orange) sites, respectively. The intermediate sites in (c) also share a face with the MoO_6 octahedra (blue).

ios involving a Mg^{2+} ion diffusing through an intermediate (tetrahedral) site that face-shares with a transition metal polyhedron lead to high migration barriers in oxides (e.g., high Mg barriers in layered NiO_2[9]), while analogous trends have been observed for Li-diffusion in disordered rock-salt structures.[34] Thus, the high Mg migration barrier in $Mg_2Mo_3O_8$ can be attributed to the intermediate O–Mg–O dumbbell configuration, which occurs in the absence of alternate low energy pathways. This indicates the importance of intermediate sites along a diffusion path, determined by the specific topology of cation sites in an anion lattice, in addition to the occurrence of the mobile cation with a non-preferred coordination and a preferentially coordinated metastable site.[9]

One of the challenges towards the development of high energy density secondary Mg batteries is the design of an ideal positive electrode, which can reversibly intercalate Mg at a high voltage with high capacities at reasonable rates. The $Mg_2Mo_3O_8$ structure used in this study was primarily motivated by the presence of Mo_3 clusters (similar to the Mo_6 clusters in the Chevrel-positive electrodes) and the occurrence of Mg in a non-preferred tetrahedral coordination (satisfying one of the design rules known in literature[9]). While Mg could be chemically extracted from the structure, albeit with significant amorphization, no electrochemical activity was observed. Further analysis using first-principles calculations revealed high E^{hull} values (structural instability) at low Mg content and high Mg migration barriers (poor bulk Mg mobility in the structure), explaining the aforementioned experimental observations. The high activation barrier for Mg diffusion in $Mg_2Mo_3O_8$ arises from the O–Mg–O dumbbell hop, reflecting the impact of intermediate sites along a diffusion pathway besides cation coordination preferences. Thus, in searches of high Mg-mobility oxide positive electrodes, a careful analysis of the diffusion pathway and the topology of cation sites is advantageous - such as identifying low-energy intermediate sites - in addition to the requirement of Mg being found in a non-preferred coordination environment.[9] Such understanding of Mg diffusion pathways will help to find suitable positive electrodes for multivalent batteries.

Acknowledgments

This work was fully supported by the Joint Center for Energy Storage Research (JCESR), an Energy Innovation Hub funded by the U.S. Department of Energy, Office of Science and Basic Energy Sciences. The authors would like to thank the National Energy Research Scientific Computing Center (NERSC) for providing computing resources. Natural Sciences and Engineering Research Council of Canada (NSERC) is acknowledged by LFN for a Canada Research Chair.

* Electronic address: gautam91@mit.edu; G. S. Gautam and X. Sun contributed equally to the work
† G. S. Gautam and X. Sun contributed equally to the work
‡ Electronic address: gceder@berkeley.edu, gceder@lbl.gov

[1] J. Muldoon, C. B. Bucur, and T. Gregory, Chem Rev **114**, 11683 (2014).
[2] H. D. Yoo, I. Shterenberg, Y. Gofer, G. Gershinsky, N. Pour, and D. Aurbach, Energy Environ. Sci. **6**, 2265 (2013).
[3] J. Muldoon, C. B. Bucur, A. G. Oliver, T. Sugimoto, M. Matsui, H. S. Kim, G. D. Allred, J. Zajicek, and Y. Kotani, Energy Environ. Sci. **5**, 5941 (2012).
[4] D. Aurbach, Z. Lu, A. Schechter, Y. Gofer, H. Gizbar, R. Turgeman, Y. Cohen, M. Moshkovich, and E. Levi, Nature **407**, 724 (2000).
[5] X. Sun, P. Bonnick, V. Duffort, M. Liu, Z. Rong, K. A. Persson, G. Ceder, and L. F. Nazar, Energy Environ. Sci. **9**, 2273 (2016).
[6] X. Sun, P. Bonnick, and L. F. Nazar, ACS Energy Lett. **1**, 297 (2016).
[7] G. Amatucci, F. Badway, A. Singhal, B. Beaudoin, G. Skandan, T. Bowmer, I. Plitz, N. Pereira, T. Chapman, and R. Jaworski, J Electrochem Soc **148**, A940 (2001).
[8] E. Levi, M. Levi, O. Chasid, and D. Aurbach, J Electroceram **22**, 13 (2009).
[9] Z. Rong, R. Malik, P. Canepa, G. Sai Gautam, M. Liu, A. Jain, K. Persson, and G. Ceder, Chem. Mater. **27**, 6016 (2015).
[10] G. S. Gautam, P. Canepa, A. Abdellahi, A. Urban, R. Malik, and G. Ceder, Chem. Mater. **27**, 3733 (2015).
[11] S.-H. Bo, C. P. Grey, and P. G. Khalifah, Chem. Mater. **27**, 4630 (2015).
[12] G. Gershinsky, H. D. Yoo, Y. Gofer, and D. Aurbach, Langmuir **29**, 10964 (2013).
[13] G. S. Gautam, P. Canepa, R. Malik, M. Liu, K. Persson, and G. Ceder, Chem. Commun. **51**, 13619 (2015).
[14] G. S. Gautam, P. Canepa, W. D. Richards, R. Malik, and G. Ceder, Nano Lett **16**, 2426 (2016).
[15] M. Liu, Z. Rong, R. Malik, P. Canepa, A. Jain, G. Ceder, and K. A. Persson, Energy Environ. Sci. **8**, 964 (2015).
[16] W. H. McCarroll, L. Katz, and R. Ward, J. Am. Chem. Soc. **79**, 5410 (1957).
[17] F. A. Cotton, Inorg. Chem. **3**, 1217 (1964).
[18] I. Brown, Acta Crystallogr., Sect. B: Struct. Sci **44**, 545 (1988).
[19] J. Barker, M. Y. Saidi, and J. L. Swoyer, *Lithiated molybdenum oxide active materials* (2005), uS Patent 6,908,710.
[20] K. Ben-Kamel, N. Amdouni, H. Groult, A. Mauger, K. Zaghib, and C. Julien, J. Power Sources **202**, 314 (2012).
[21] J. Ma, Y.-N. Zhou, Y. Gao, X. Yu, Q. Kong, L. Gu, Z. Wang, X.-Q. Yang, and L. Chen, Chem. Mater. **26**, 3256 (2014).
[22] J. T. Incorvati, L. F. Wan, B. Key, D. Zhou, C. Liao, L. Fuoco, M. Holland, H. Wang, D. Prendergast, K. R. Poeppelmeier, et al., Chem. Mater. **28**, 17 (2015).
[23] W. Kaveevivitchai and A. J. Jacobson, Chem. Mater. **28**, 4593 (2016).
[24] A. R. Wizansky, P. E. Rauch, and F. J. Disalvo, Tech. Rep., DTIC Document (1989).
[25] H. M. Rietveld, J Appl Crystallogr **2**, 65 (1969).
[26] P. Canepa, S. Jayaraman, L. Cheng, N. N. Rajput, W. D. Richards, G. S. Gautam, L. A. Curtiss, K. A. Persson, and G. Ceder, Energy Environ. Sci. **8**, 3718 (2015).
[27] P. Canepa, G. S. Gautam, R. Malik, S. Jayaraman, Z. Rong, K. R. Zavadil, K. Persson, and G. Ceder, Chem. Mater. **27**, 3317 (2015).
[28] L. F. Wan, B. R. Perdue, C. A. Apblett, and D. Prendergast, Chem. Mater. **27**, 5932 (2015).
[29] X. Sun, V. Duffort, B. L. Mehdi, N. D. Browning, and L. F. Nazar, Chem. Mater. **28**, 534 (2016).
[30] O. Mizrahi, N. Amir, E. Pollak, O. Chusid, V. Marks, H. Gottlieb, L. Larush, E. Zinigrad, and D. Aurbach, J. Electrochem. Soc. **155**, A103 (2008).
[31] A. Jain, S. P. Ong, G. Hautier, W. Chen, W. D. Richards, S. Dacek, S. Cholia, D. Gunter, D. Skinner, G. Ceder, et al., APL Mater **1**, 011002 (2013).
[32] P. Vlek and W. Lindsay, Soil Sci. Soc. Am. J. **41**, 42 (1977).
[33] L. W. Staples, Am. Mineral. **36**, 609 (1951).
[34] A. Urban, J. Lee, and G. Ceder, Adv. Energy Mater. **4**, 1400478 (2014).

TABLE II: The E^{hull} values (in meV/atom) and the corresponding decomposition products are listed as a function of Mg content in the Mo_3O_8 structure, as obtained from the Materials Project database. The comments column indicates available experimental observations.

Composition	E^{hull}	Decomposition products	Comments
$Mg_2Mo_3O_8$	51	MoO_2 + MgO	Chemically synthesizable
$MgMo_3O_8$	180	MoO_2 + $MgMoO_4$	–
Mo_3O_8	330	MoO_2 + Mo_8O_{23}	Naturally amorphous[32,33]